

IV.7. PROMOTED IRON CATALYSTS. CHARACTERIZATION BY THERMAL ANALYSIS (Komandur V. R. Chary, Diane R. Milburn, and Burtron H. Davis).

IV.7.1. ABSTRACT

The effects of metal and alkali promoters on precipitated iron oxide Fischer-Tropsch catalyst precursors are examined using thermal gravimetry (TG) and differential thermal analysis (DTA). A distinct exotherm corresponding to what appears to be the transformation from FeOOH to Fe_2O_3 is observed for unpromoted and promoted iron oxides where the promoter's ionic radius is less than approximately 0.7\AA . The heat released during the exotherm is similar for unpromoted and promoted iron oxides corresponding to this size range. For promoters having ionic radii larger than 0.7\AA , the exotherm occurs over a broad temperature range. Silica exhibits a unique propensity to stabilize against this transition, and appears to be present as two species. Increased loadings of Si cause a shift from the sharp, narrow temperature range exotherm to the broad transition observed for promoters with larger ionic radii.

IV.7.2. INTRODUCTION

Iron catalysts find significant application in the ammonia synthesis (IV.7.1) and Fischer-Tropsch synthesis (IV.7.2). In both of these applications the iron catalyst is promoted, and usually multiply promoted. Structural promoters, such as SiO_2 and Al_2O_3 , are added primarily to improve or maintain surface area, and thereby to extend the life of the catalyst. Alkali or alkaline-earth promoters are added to improve activity, selectivity and/or catalyst life. In many instances, the catalyst is prepared by precipitation of the iron as a hydrous oxide, oxyhydroxide or hydroxide. Promoters

may be incorporated during the precipitation step, during the washing step or by impregnation following the washing step. The impregnation may be done prior to adding the catalyst to the reactor, following a pretreatment, or added *in-situ* prior to or during the conversion.

One or more precondition steps are usually necessary before using the material for a catalytic reaction. This is true even for the unusual case where the precipitated Fischer-Tropsch catalyst is heated to the reaction temperature in the synthesis gas. Much more frequently, the dried material will be subjected to one or more heat treatments prior to or during the preconditioning process.

It has been observed that the surface area of calcined promoted iron oxide catalysts varies with the size of the metal promoter (IV.7.3). Those promoters with an ionic radius smaller than iron produce a calcined material with a surface area higher than iron oxide while materials that contain a promoter with an ionic size larger than iron have a lower surface area than iron oxide. Since calcination is a common step in the preparation of most iron catalysts in both experimental laboratory and commercial scale synthesis, it is of interest to learn how a variety of promoters impact the thermal events that occur as the catalyst precursor is subjected to thermal treatments. The present paper is concerned with defining the impact of a variety of promoters on the weight loss, thermal events and the extent of heat liberated in the thermal events.

IV.7.3. EXPERIMENTAL

Unpromoted $\text{Fe}(\text{OH})_3$ was prepared by precipitation at $\text{pH} = 8$ from an iron(III) nitrate solution by addition of ammonium hydroxide. The resulting dark brown precipitate was then filtered and washed four times with distilled-deionized water and

dried in flowing air at 100°C for 24 hours. Samples promoted with metal oxide were prepared under similar conditions using a 15.6M ammonium hydroxide solution to precipitate from a solution of iron nitrate and the appropriate metal nitrate. In several cases the pH exceeded 8.5. The silica promoted iron was coprecipitated from iron nitrate and silica gel, prepared from the hydrolysis of tetraethylorthosilane. Metal promoter loadings were 6% by weight based on the stable oxide following calcination in air. Potassium was added to alumina or silica promoted samples by incipient wetness impregnation to achieve 1, 3 and 6 wt.% K.

Differential thermal analysis (DTA) and thermogravimetry (TG) were performed using a Seiko SSC/5200 instrument. Typical sample size was 20-30 mg with aluminum oxide used as a reference. Each sample was heated in a He atmosphere from 25°C to 900°C at a rate of 20°C per minute and held for 10 minutes before cooling. A tin standard was analyzed under identical conditions in order to calculate the heat evolved during the exotherms observed for iron and promoted iron samples. These data are listed in Table IV.7.1.

X-ray diffraction patterns were obtained using a Phillips model 3100 instrument fitted with a $\text{CuK}\alpha$ radiation source.

IV.7.4. RESULTS

The weight loss and differential thermal analysis curves for the iron-based samples indicate that essentially all of the weight loss for the unpromoted iron oxide (the sample will be referred to as though it was an oxide although it is realized that the initial material may be amorphous to X-rays or is a crystalline form of FeOOH) are those expected for the dehydration of a hydrous material rather than that of a salt

hydrate such as, for example, $\text{CaSO}_4 \cdot \text{H}_2\text{O}$. There is a gradual weight loss upon heating to about 400°C ; above this temperature there is essentially no weight loss (Figure IV.7.1). The weight loss corresponds to 10.5% of the initial sample suggesting a transformation from FeOOH to Fe_2O_3 (theoretical weight loss of 10.14%). During the period of the weight loss, the endothermic event is consistent with the gradual loss of water. However, following the dehydration period, an exothermic event occurs that is centered at 442°C . This event has been observed in other systems and has been termed a "glow phenomenon;" this usually occurs through a sintering of small particles to produce larger particles with a lower surface area (IV.7.4, IV.7.5). The exotherm for the unpromoted iron oxide corresponds to 4.0 kCal (16.7 kJ)/mole of Fe_2O_3 , a value in line with that expected to be associated with the loss of surface area. A sample of the unpromoted iron oxide was amorphous to X-rays following calcination at 300°C for 4 hrs. but was converted to crystalline $\alpha\text{-Fe}_2\text{O}_3$ during heating for 4 hrs. at 400°C .

All of the samples listed in Table IV.7.1 exhibited weight loss curves that were similar to the unpromoted sample in that essentially all of the weight loss occurred prior to the exothermic event. Furthermore, the temperature-weight loss curve for all of the materials exhibited a similar shape, and all samples attained a constant weight at about the same temperature (less than 400°C as shown in Figure IV.7.1). No indication of a weight loss was observed that could be associated with the conversion of a supported hydrous oxide such as, for example, hydrous chromium oxide. No correlation exists between weight loss and temperature of the exotherm or ionic radius of the promoter metal.

When the ionic radius of the metal promoter was much larger than that of iron, the exotherm tended to become less distinct. For the chromium promoter (ionic radius of 0.69\AA versus 0.64\AA for iron) there is a distinct exothermic thermal event at 480°C (Figure IV.7.2).. The results with magnesium and tungsten promoters, with ionic radii slightly larger than iron, were very similar to those shown in figure 2 for chromium. However, for the samples promoted by the four metals with the largest ionic radii shown in Table IV.7.1 (Zr, Ca, Th, and Ba), there was no prominent, distinct exothermic event. The trace in figure 3 is typical of the type of DTA curves obtained for the materials promoted by the metals with the four largest ionic radii.

It appears that the temperature of the exotherm remains approximately constant and then declines as the ionic radius of the metal promoter approaches that of iron (Figure IV.7.4, Table IV.7.1). The exotherm temperature then increases as the ionic radius of the promoter increases beyond that of iron; the material promoted with magnesium appears, however, to exhibit a much higher exotherm temperature than anticipated by the trend established with the ionic radii. Repeat runs show that the heat liberated for the Mg promoted material is reproducible. The exotherm temperatures for the promoters with the largest radii are difficult or impossible to identify, due to the absence of a sharp peak.

The heat liberated during the exothermic event was about the same for the unpromoted iron oxide and for many of the promoted materials (23-26 cal/g; 96-109 J/g) (Figure IV.7.5). Less heat was liberated during the exothermic event for the two samples promoted with metals with the lowest ionic radii than for iron oxide. For the four materials promoted with the metals having the largest ionic radii, the heat

liberated could not be estimated due to the poor definition of the exothermic event. It appears likely that the inability to observe the exothermic event with the materials promoted with the metals with the four largest ionic radii was due to the fact that the crystallization occurred over a broad temperature region in contrast to the materials that showed the transformation in a distinct, narrow temperature region. Silicon is especially effective in retaining the iron oxide in an amorphous state, and this is the likely reason for the low value of the exotherm for the silicon promoted material. Furthermore, the data for the silicon promoted material suggest that silicon is present in at least two forms. The amorphous structure is retained for the material containing 6% SiO₂ even following calcination in air at 500°C for four hours; presumably the fraction of Si that stabilizes the amorphous phase of iron oxide behaves much as that of, for example, thorium so that the crystallization occurs over a broad temperature range and the exotherm is not observed. On the other hand, some of the Si must be present in a form that increases the temperature of the exothermic event and transforms over a narrow temperature range. Based upon the heat liberated during the sharp exothermic event for the material promoted with silicon and for the unpromoted iron oxide, it is estimated that about 15% of the silicon is present in the form that leads to the distinct, narrow temperature region exothermic event.

A series of Si and Al promoted materials were prepared to contain 1, 3 and 6 wt.% of the metal oxide promoter. It appears that the weight loss during heating to 900°C is essentially the same for the unpromoted material and the ones containing 3 and 6 wt.% promoter loadings. However, in both instances the materials that contained only 1 wt.% promoter lost less (20-30%) weight than the unpromoted material. It is not apparent why this should be the case. The temperature of the

exothermic event increases with increasing loading of the promoter for both Si and Al; however, each succeeding addition, on an equivalent weight basis, is less effective in increasing the temperature of the exotherm (Figure IV.7.5). The data shown in figure 5 make it apparent that of the two promoters, Si is more effective in increasing the exotherm temperature; furthermore, it appears that Al approaches a limiting effect at the 6 wt.% loading but that further increases in Si content should continue to cause significant increases in the temperature of the exotherm. The heat liberated during the distinct, narrow temperature range exotherm increases with the addition of the Al promoter and then declines slightly so that the heat released by the material containing 6 atomic% Al is about the same as that of the unpromoted iron oxide (Figure IV.7.6). The heat released declines as Si is incorporated in the iron oxide. As indicated above, it appears that Si is incorporated in the material in at least two forms. The decrease in the heat liberated with increasing Si content indicate that fraction of the added Si that is incorporated to produce the distinct, narrow temperature range exothermic event decreases as the Si loading increases. The decrease in the heat liberated for the 1 atomic% Si sample indicates that 84% of the added Si is of the form that contributes to the higher-temperature, narrow-range exothermic event; this is 56% for the material with 3 atomic% Si and decreases to less than 10% for the material containing 6 atomic % Si.

Alkali promoters are utilized in Fischer-Tropsch catalysts in addition to silica, alumina, etc. The data (Figure IV.7.7) indicate that the addition of 1 or 3 wt.% K to the silica or alumina promoted materials cause only a slight increase in the exotherm temperature. However, in most cases, the addition of alkali causes a dramatic

decrease in the heat liberated during the narrow temperature-range exotherm event (Figure IV.7.8). In the case of the alumina promoted material, the addition of potassium always causes a dramatic decrease in the heat liberated during the well-defined exothermic event even though the temperature at which this event occurs does not change significantly. Thus, it appears that the added alkali interacts with the alumina promoter. Furthermore, the fact that the heat liberated decreases with increased K indicates that a fraction of the AlO_2^- that would interact with iron oxide in the absence of K^+ , has been altered by interacting with K^+ . The trend in the decrease of heat liberated indicates that the iron oxide-alumina- K^+ interaction varies over a wide range in order to spread the exothermic event over a wide temperature range.

The situation with silica differs from that of alumina. It appears that the alkali has much less impact upon the amount of heat liberated in the well-defined region. This is consistent with the view that the silica, unlike alumina, is present in a range of species even in the absence of K^+ .

IV.7.4. DISCUSSION

The presence of a promoter dramatically alters the thermal conversions of a precipitated iron oxide catalyst precursor. In general, the presence of the promoter causes an increase in the temperature at which the exotherm occurs from that of the unpromoted iron oxide. As the mismatch of ionic radius between the promoter and iron ion increases, so does the temperature at which the exothermic event occurs. Presumably the fraction of the promoter that is effective in increasing the exotherm temperature is that which is present on the surface of the precipitated hydrous iron oxide particles. If this is the case, then the fraction of the promoter that is on the

surface increases as the ionic radius of the added metal ion becomes larger than that of iron. It is becoming increasingly apparent that the addition of anions, such as SO_4^{2-} , MoO_4^- , WO_4^- , etc., to the surface of a hydrous metal oxide inhibits the loss of surface area and the occurrence of the "glow phenomenon," or events that are similar to the glow phenomena (IV.7.6-IV.7.8). However, it does not appear that all of the promoters having an ionic radius larger than iron would be present on the surface as an oxygen containing anion cluster. For example, it is likely that Ca^{2+} and Ba^{2+} would not be present on the surface as an anion cluster but rather as the cation. It therefore appears that these larger cations may also function by causing the anion cluster to be formed from the hydrous iron oxide through the formation of a surface structure that at least resembles $\text{Ca}_3(\text{FeO}_3)_2$ or CaFeO_2 .

All of the promoters employed in the study having an ionic radius smaller than 0.7\AA interact in such a way that a distinct, narrow-range exothermic event occurs during the heating of the catalyst precursor. The heat released during this exothermic event is similar for nearly all of these promoters, and is very close to that of the unpromoted iron oxide. Therefore, the transformation responsible for the exotherm is a common one for the unpromoted and most or all of this grouping of promoted iron oxide catalyst precursors. The promoter does not cause an event to occur which is distinct from that observed in the unpromoted material, but rather provides a barrier that must be overcome for the event to occur. For the promoters with an ionic radius larger than about 0.7\AA , the exotherm is difficult to observe, presumably because the transformations leading to the exothermic event occur over a wide range of temperatures. This implies that the promoters having larger ionic radii do not form a

specific compound but form instead a nearly continuous range of structures whose interactions between the iron oxide and the promoter varies almost continuously.

One could anticipate that Si and Al promoters should produce similar effects and that the thermal transformations of catalyst precursors containing either of these promoters should be similar. That expectation clearly does not coincide with the experimental observations. Both promoters do cause an increase in the temperature at which the exothermic event occurs; however, the Si promoter is more effective in doing this than is the Al promoter. The Al promoter causes an initial increase in the heat liberated during the exothermic event, but the heat liberated by a material containing 6 atomic% Al is about the same heat as the unpromoted iron sample. By analogy with other promoters, such as SO_4^{2-} , this implies that Al is present as the AlO_2^- anion at the conditions of the iron precipitation, and that this anionic species coats the surface of the iron oxide particles. However, it appears that silica is functioning in two roles. A portion of the silica causes an effect resembling the promoters with larger ionic radii by spreading the exothermic event over a wide range of temperatures not measurable by the experimental technique used in the present study. Another portion of the silica appears to behave as would be expected for a material with its ionic radius, causing the exothermic event to occur over a narrow temperature range. Thus, it appears that as the Si loading in the catalyst precursor is increased, an increasingly smaller fraction of the Si acts as the SiO_2^- anion to produce the narrow temperature range exotherm. Concurrently, an increasingly larger fraction appears to be present in a form that functions as a cation which could stabilize against the transformation by inducing the formation and bonding with a structure such as FeO_2^+ . This view of these two promoters suggests that Al should

cover a larger fraction of the surface of the iron oxide catalyst than a similar amount of Si would. The activity of the iron catalyst promoted with Al and carbided with CO begins to decrease as the Al loading reaches about 5 atomic%. On the other hand, the activity of the Si promoted catalyst does not decrease even as the Si loading is increased to 15 atomic%. These activity measurements (IV.7.9) are consistent with the view that silica does not cover the surface of the iron oxide and the iron carbide catalyst resulting from the carbiding procedure, as effectively as the Al promoter does. One explanation for this is for the fraction of the Si promoter that functions as the cation species to be a positively charged silica polymer, Si_xO_y^+ . Another would be the incorporation of Si in the bulk structure of the iron oxide.

IV.7.5. ACKNOWLEDGEMENT

The authors acknowledge the financial support of this work by the Department of Energy contract No. DE-AC22-91PC90056 and by the Commonwealth of Kentucky.

IV.7.6. REFERENCES

- IV.7.1. P. H. Emmett in "Battelle," *Inst. Mater. Sci. Colloq.*, **9**, 3 (1975).
- IV.7.2. R. B. Anderson, "The Fischer-Tropsch Synthesis," Academic Press, New York, 1984.
- IV.7.3. D. Milburn, K. V. R. Chary and B. H. Davis, submitted.
- IV.7.4. H. B. Weiser, "The Hydrous Oxides," McGraw-Hill, New York, 1926, pg. 79.
- IV.7.5. R. Srinivasan and B. H. Davis, *J. Colloid Interface Sci.*, **156**, 400 (1993).
- IV.7.6. T. Yamaguchi and K. Tanabe, *Materials Chem. and Phys.*, **16**, 67 (1986).
- IV.7.7. R. Srinivasan, D. Taulbee and B. H. Davis, *Catal. Lett.*, **9**, 1 (1991).
- IV.7.8. L-M. Tau, R. Srinivasan, R. J. De Angelis, T. Pinder and B. H. Davis, *J. Mater. Res.*, **3**, 561 (1988).
- IV.7.9. B. H. Davis, unpublished results.

Table IV.7.1

Exotherm Temperature and Heat Evolved During Crystallization of Iron Catalysts
Containing 6 wt.% of Various Metal Oxide Promoters

<u>Promoter</u>	<u>Precursor</u>	<u>Ion</u>	<u>Ionic Radius (Å)</u>	<u>ΔH (cal.g⁻¹)</u>	<u>Temperature of exotherm (°C)</u>
B ₂ O ₃	Boric Acid	B ³⁺	0.20	18.33	575
SiO ₂	Tetraethyl orthosilane	Si ⁴⁺	0.41	3.62	620
Al ₂ O ₃	Aluminum ^{III} nitrate	Al ³⁺	0.50	26.05	572
MnO ₂	Manganese ^{III} nitrate	Mn ²⁺	0.54	25.10	537
V ₂ O ₅	Ammonium metavanadate	V ⁵⁺	0.59	23.16	522
MoO ₃	Ammonium heptamolybdate	Mo ⁶⁺	0.62	23.16	491
None	---	Fe ³⁺	0.64	25.10	442
MgO	Magnesium nitrate	Mg ²⁺	0.65	23.16	573
WO ₃	Ammonium metatungstate	W ⁶⁺	0.68	23.16	512
Cr ₂ O ₃	Chromium ^{III} nitrate	Cr ³⁺	0.69	30.21	480
ZrO ₂	Zirconium oxynitrate	Zr ⁴⁺	0.79	--	(broad)
CaO	Calcium nitrate	Ca ²⁺	0.99	--	~ 616 (broad)
ThO ₂	Thorium nitrate	Th ²⁺	0.99	--	~ 541 (broad)
BaO	Barium nitrate	Ba ²⁺	1.35	--	~ 585 (broad)

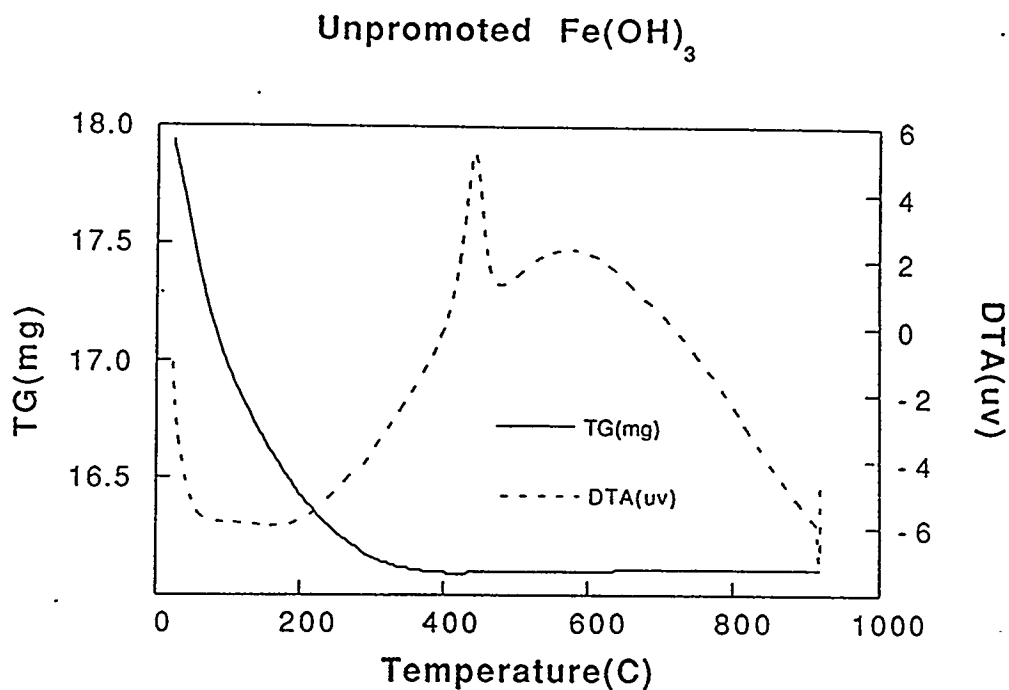


Figure IV.7.1. Thermal gravimetric (TG) and differential thermal analysis (DTA) curves for the unpromoted iron oxide sample.

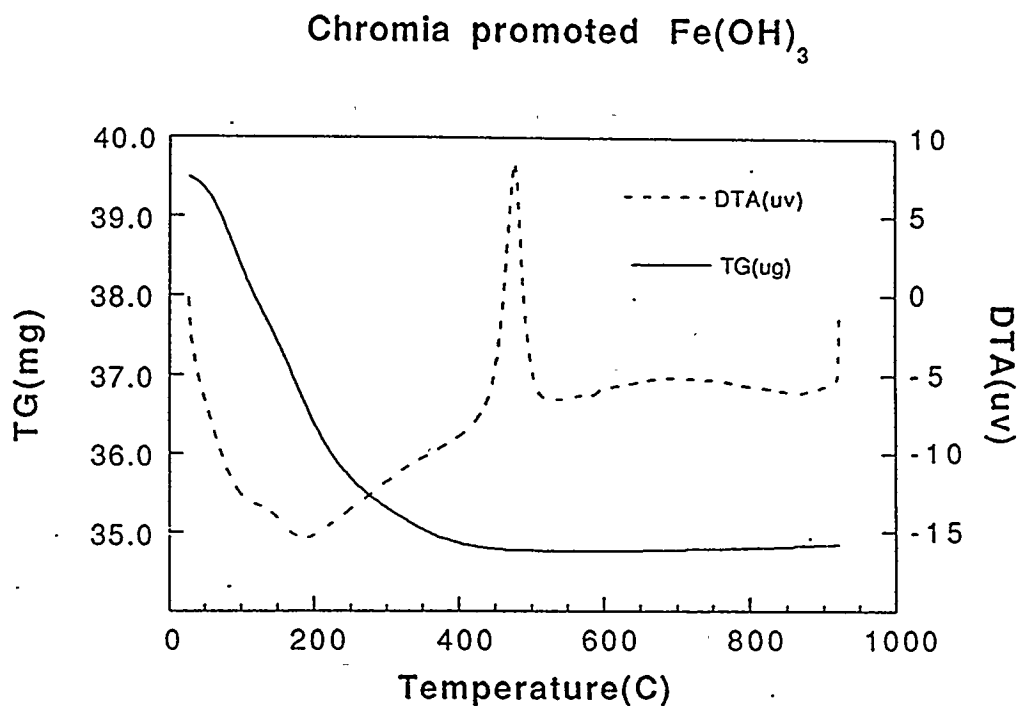


Figure IV.7.2. Thermal gravimetric (TG) and differential thermal analysis (DTA) curves for the 6% chromium oxide promoted iron oxide.

BaO promoted $\text{Fe}(\text{OH})_3$

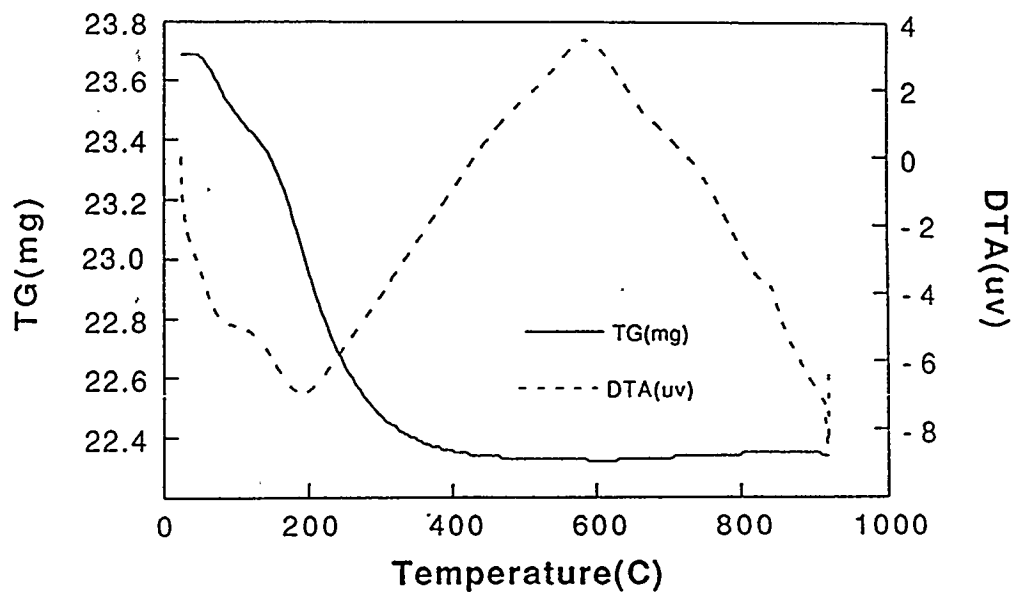


Figure IV.7.3. Thermal gravimetric (TG) and differential thermal analysis (DTA) curves for the 6% barium oxide promoted iron oxide.

Effect of 6% Promoter Addition on Exotherm Temperature of Precipitated Iron

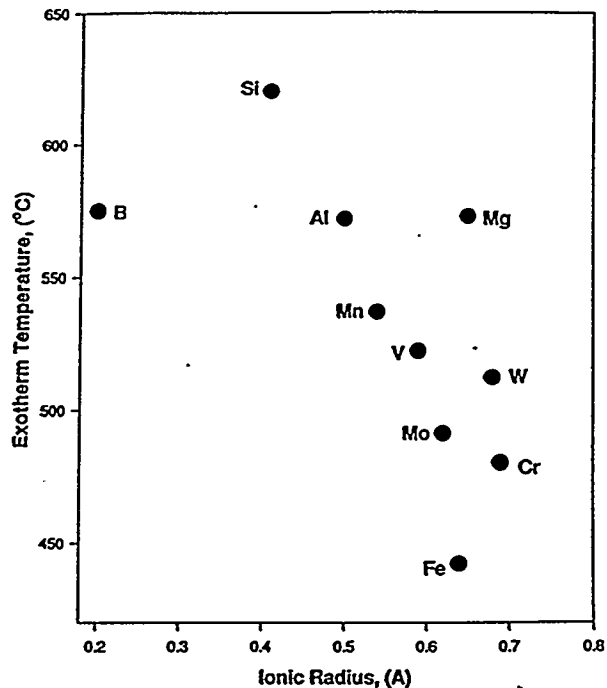


Figure IV.7.4. Exotherm temperature for 6% metal oxide promoted and unpromoted iron oxides.

Effect of Metal Loading on Exotherm Temperature of Precipitated Iron Catalyst Precursors

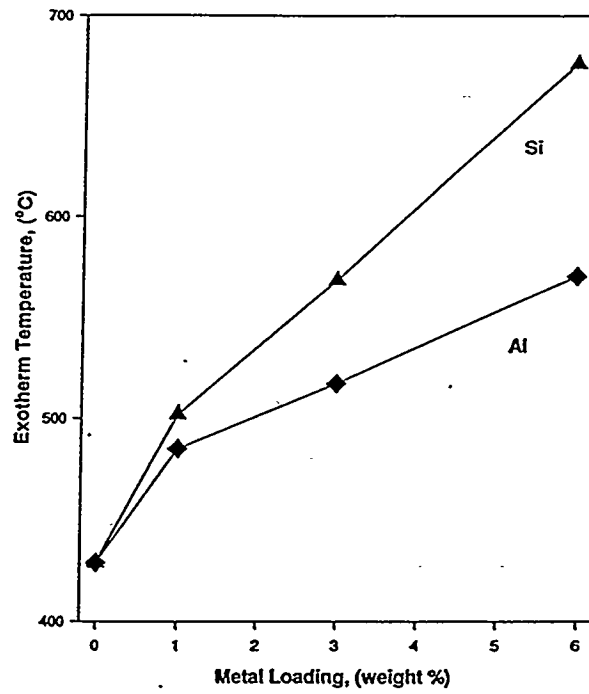


Figure IV.7.5. Exotherm temperature for Si and Al promoted iron oxides.

Effects of Metal Promoter Addition on Heat Liberated from Precipitated Iron

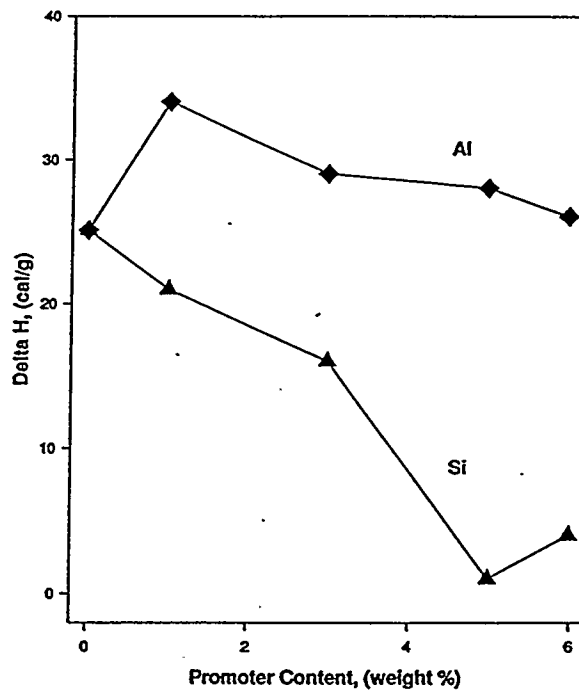


Figure IV.7.6. Heat liberated during exothermic event for Si and Al promoted iron oxides.

Effects of K Addition on Exotherm Temperature of Promoted Iron Catalysts

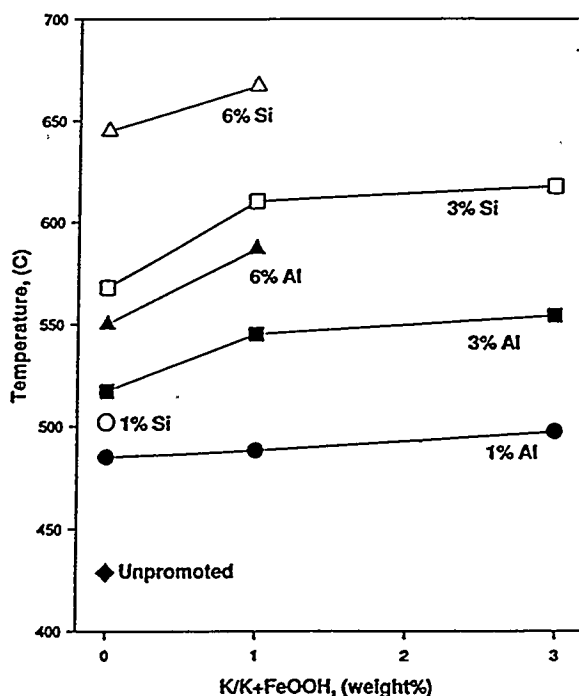


Figure IV.7.7. Exotherm temperature for K and Si or Al doubly promoted iron oxides.

Effects of K Addition on Heat Liberated From Promoted Iron Catalysts

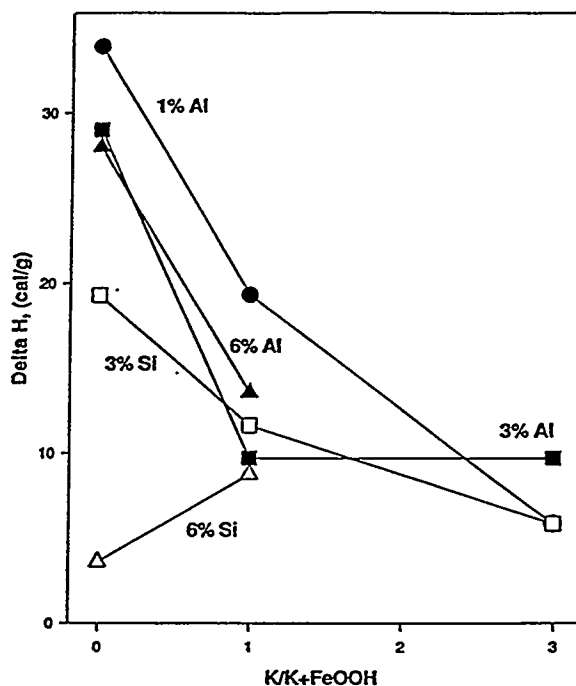


Figure IV.7.8. Heat liberated during the exothermic event for K and Si or Al doubly promoted iron oxides.